


A CIRCULAR ECONOMY APPROACH FOR CUPRIAVIDUS NECATOR DSM 545 BIOSYNTHESIS OF POLY(3-HYDROXYBUTYRATE)

S. Bellini a,b, T. Tommasi a and D. Fino* a,b

^a Politecnico di Torino, Department of Applied Science and Technology, Torino, Piemonte, Italy ^b Istituto Italiano di Tecnologia, Center for Sustainable Future Technologies, Torino, Piemonte, Italy *corresponding author, (presenting author e-mail: silvia.bellini@polito.it)



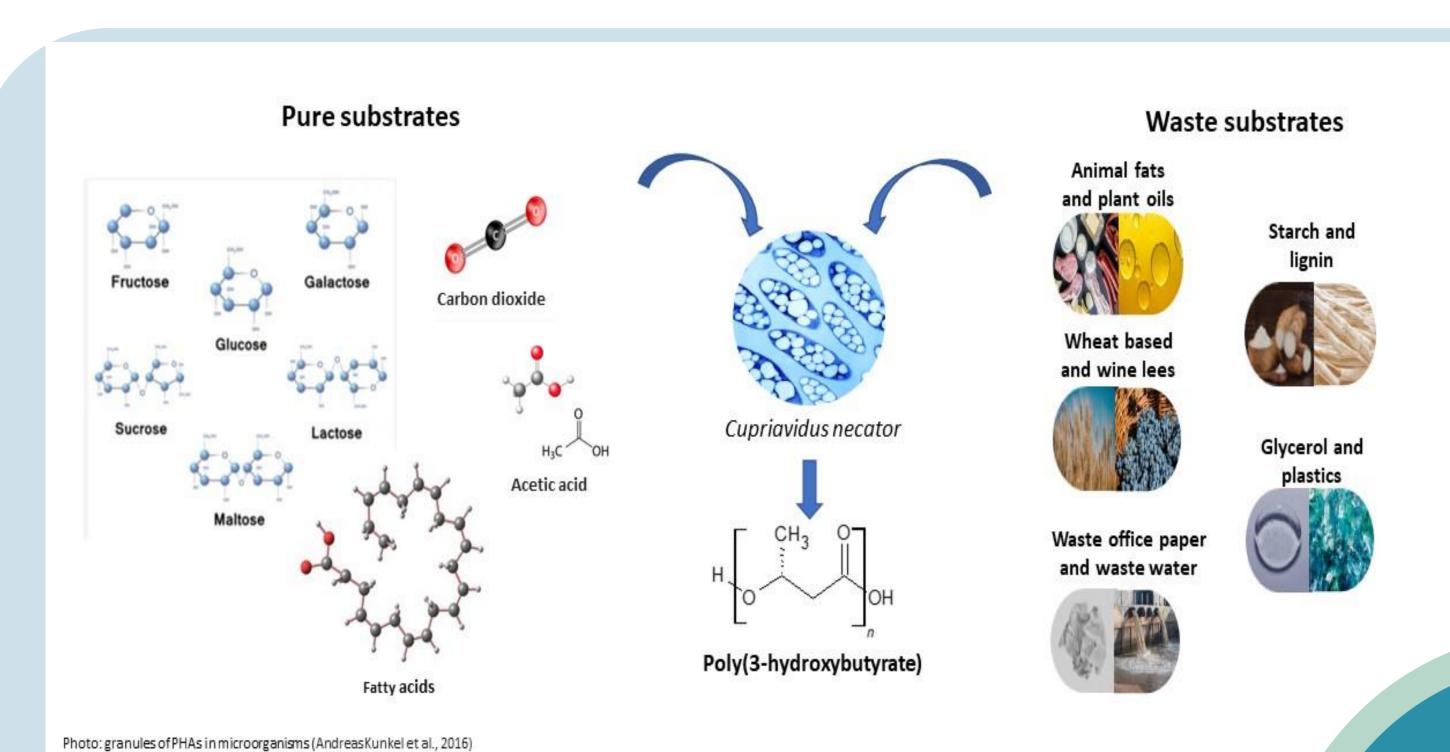

- > Cupriavidus necator produces large amounts of the polyester poly (3hydroxybutyric acid), or PHB.
- > It is a versatile bacterium: it can grow both autotrophically and heterotrophically, and on a wide range of organic substrates, including waste feedstocks (Bellini et al., 2022).
- In this work, C. necator DSM 545 strain has been fermented to reach high yield of PHB by using two waste substrates.
- > Circular economy approach for bacterial PHB biosynthesis
- > This research is part of the PRIME project (Processi e pRodotti Innovativi di chiMica vErde), promoted by Novamont® and Piedmont Region.


Introduction


Data

Materials


& Methods

- ✓ 1L bioreactor Sartorius®, working volume 0,5 L, pH 6.8, 30°C, vvm 0,5.
- ✓ C. necator DSM 545 grown using a growth medium containing a carbon source, phosphate, sulphate and magnesium sources, and metals (Mozumder et al. 2014.
- ✓ Biomass sampled at 15, 24, 36, 40, 45 and 48 hours.
- **✓ Two different carbon waste sources:**
- 1. a syrup (glucose and fructose in equal amount) from PRIME project supply chain (partner Sedamyl[©])
- 2. the sterilized and concentrated waste medium of an acetogenic bacterium (Acetobacterium woodii) fermentation containing acetate.
- ✓ Sugars and acetate in the medium and PHB concentration (extracted by acid) digestion using sulphuric acid 96%): analyzed at HPLC using a Resex18 column and a mobile phase of H_2SO_4 5 mM (flow rate of 0.7 mL/min).

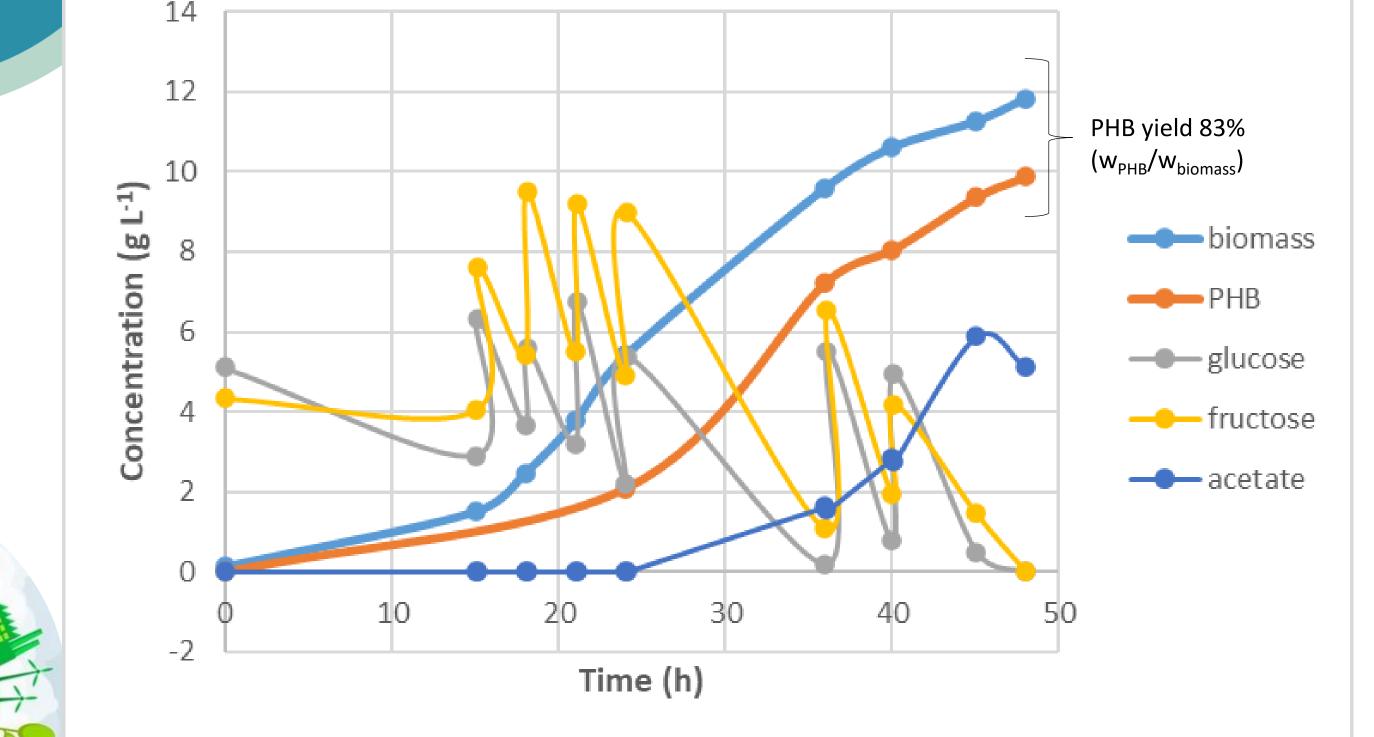

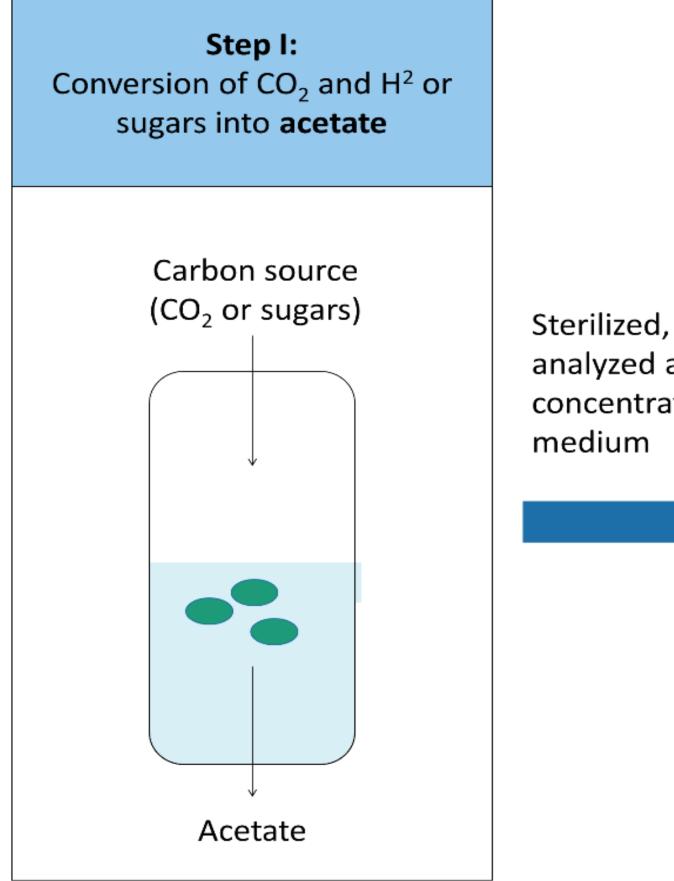

Acetobacterium woodii

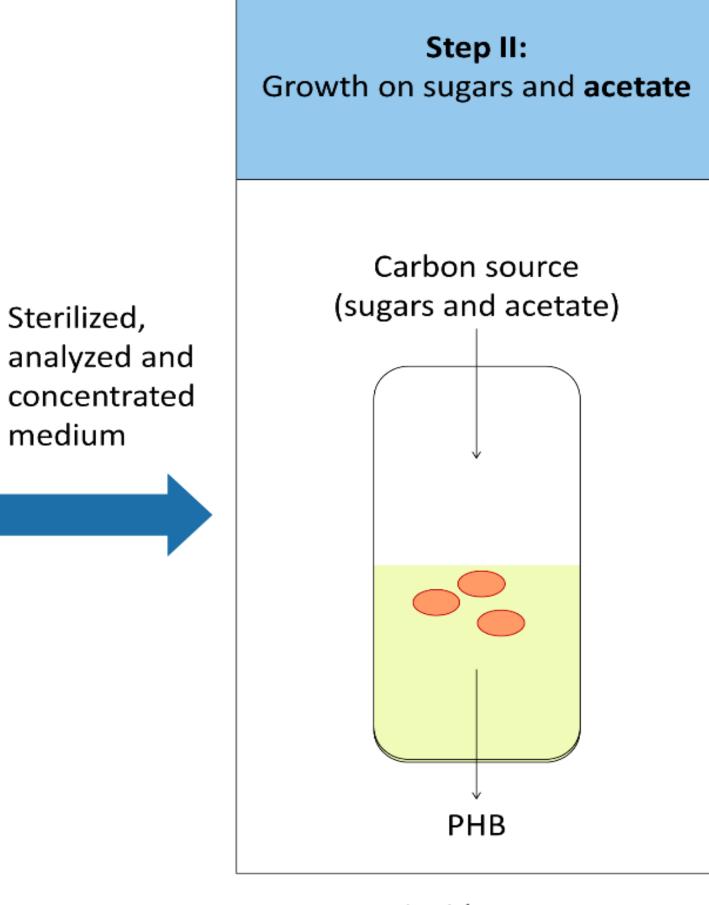

Cupriavidus necator

Results & Discussion

- > The graph shows the fermentation of *C. necator* DSM 545 performed through a "two-step" fermentation strategy, as shown in the scheme on the left.
- > Sedamyl[©] syrup (containing glucose and fructose equal concentrations) has been furnished at different concentrations during the whole fed-batch fermentation ("spike feeding").
- > After 24 hours, spike feeding of the acetogenic bacterium medium containing acetate (2 g L⁻¹ each feed).
- > The highest PHB concentration, almost 10 g L⁻¹, has been reached after 48 hours of fermentation and the biomass reached about 12 g L-1 at the same hour.
- > 83% of PHB content, W_{PHB}/W_{biomass}.
- > PHB is mainly accumulated in *C. necator* under unbalanced growth conditions, e.g. when shortage of N and P occur.

Conclusions

- ✓ High concentration of PHB and biomass: yield of 83% of biopolymer (w/w), using valuable waste substrates, using a circular economy approach.
- ✓ C. necator DSM 545 easily convert glucose, fructose and acetate into PHB.
- ✓ Optimization of fermentation operative conditions:
- A three phases C/N ratio fermentation approach (three different concentrations of C and N and relative ratio) could be used to test PHB biosynthesis improvement (Garciagonzalez and Wever, 2018).
- ii. Exponential feeding and an alkali-addition monitoring strategies (Mozumder et al., 2014)
- iii. Utilization of carbon dioxide waste (e.g. industrial gas-off) as carbon source for acidogenic bacterium fermentation, to improve the whole Life Cycle Assessment analysis of the process.

Bibliography

- Bellini S., Tommasi T., Fino D., (2022). Poly(3-hydroxybutyrate) biosynthesis by Cupriavidus necator: a review on waste substrates utilization for a circular economy approach. Bioresource Technology Reports, Vol. 17.
- Md. Salatul Islam Mozumder, Heleen De Wever, E.I.P.V., and A, L.G.-G. (2014). A robust fed-batch feeding strategy independent of the carbon source for optimal polyhydroxybutyrate production. Process Biochem. Vol. 49, Issue 3 49, 365–373.
- Kourmentza, C., Pl, J., Venetsaneas, N., Burniol-figols, A., Varrone, C., Gavala, H.N., and Reis, M.A.M. (2017). Recent Advances and Challenges towards Sustainable Polyhydroxyalkanoate (PHA) Production. Bioingenireeing 1–43.
- Garcia-gonzalez, L., and Wever, H. De (2018). Acetic Acid as an Indirect Sink of CO2 for the Synthesis of Polyhydroxyalkanoates (PHA): Comparison with PHA Production Processes Directly Using CO 2 as Feedstock. Appl. Sci.













